

EFFECT OF TOOL GEOMETRY ON MECHANICAL PROPERTIES OF FRICTION STIR WELDING OF ALUMINIUM ALLOY AA2014-T6

Mr.Wakchaure P. N.¹, Prof.Dr.Borkar B. R.² Mr.Tajane R. S.³

^{1&2} Department of Production Engineering, Amrutvahini College of Engineering, Sangamner.

³ Department of Mechanical Engineering, Amrutvahini College of Engineering, Sangamner.
prakesh.wakchaure293@gmail.com

Abstract:—

Friction Stir Welding (FSW) was invented by Wayne Thomas at TWI (The Welding Institute), and the first patent applications were filed in the UK in December 1991 for butt and lap welding of metals and Plastics. FSW is a solid state welding process and joining similar or dissimilar metals in which the relative motion between the tool and the work piece produces heat which makes the material of two edges being joined by plastic atomic diffusion. In this work newly design and developed tool pin profile is considered to study the effect of this tool geometry on mechanical properties of friction stir weldments of AA 2014-T6 aluminium alloy using Taguchi's one parameter at-one-time approach. The various process parameters was considered such as tool rotational speed (TRS), weld speed (WS) and tilt angle for friction stir weldments of AA 2014-T6 aluminium. From the result it is observed that the parameters i.e. TRS (710 rpm), WS (49 mm/min), Tilt Angle (2°) gives highest tensile strength.

Keywords: Friction Stir Welding, Tool Rotation Speed, Weld Speed, Tilt Angle.

I. INTRODUCTION

Friction stir welding (FSW) is a relatively new solid state welding process which is used for butt joints. FSW was invented by The Welding Institute (TWI), Cambridge, UK in 1991 and has emerged as a new process for welding of aluminum alloys. This process has made possible to weld a number of aluminum alloys that were previously not recommended (2000 series & copper containing 7000 series aluminum alloys) for welding. Because the material subjected to FSW does not melt and re-solidify, the resultant weld metal is free of porosity with lower distortion. An added the advantage that it is an environmentally friendly process. FSW is a solid state, localized thermo mechanical, joining process.

FSW is a simple process in which a rotating cylindrical tool with a shoulder and a profiled pin is plunged into the abutting plates to be joined and traversed along the line of the joint. The plates are tightly clamped on to the bed of the FSW equipment to prevent them from coming apart during welding. A cylindrical tool rotating at high speed is slowly plunged into the plate material, until the shoulder of the tool touches the upper surface of the material. A downward force is applied to maintain the contact. Frictional heat, generated between the tool and the material, causes the plasticized material

to get heated and softened, without reaching the melting point. The tool is then traversed along the joint line, until it reaches the end of the weld [1].

As the tool is moved in the direction of welding, the leading edge of the tool forces the plasticized material, on either side of the butt line, to the back of the tool. In effect, the transferred material is forged by the intimate contact of the shoulder and the pin profile. In order to achieve complete through-thickness welding, the length of the pin should be slightly less than the plate thickness, since only limited amount of deformation occurs below the pin. The tool is generally tilted by 2-4°, to facilitate better consolidation of the material in the weld [2].

In FSW, the tool typically consists of a cylindrical shoulder with a profiled probe, also called the pin. The material or materials being welded can be called the work piece, part, sample, or plate. The joint where the samples are abutted will be referred to as the weld line. The part used to support and clamp the sample is called the backing plate, backing bar, or anvil. The tool rotates at an angular velocity given in revolutions per minute (rpm), which will be referred to as tool rotational speed (TRS). The translational velocity at which the tool travels along the weld line is called the feed rate or weld speed (WS), and will be given in millimeter per second (mm/s) or inches per minute (ipm).

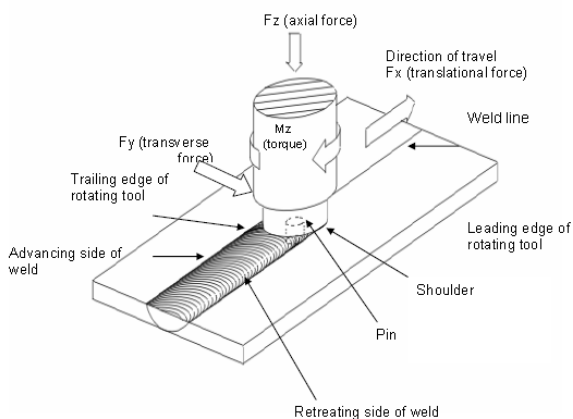


Fig. 1 Schematic of the FSW Process [3]

The side of the weld where the angular velocity and forward velocity of the pin tool are additive is called the advancing or leading side. The other side where the angular velocity and translational velocity are in opposite directions is called the trailing or retreating side. As shown in Fig. 1.1, forces act in three dimensional spaces. The force along the X-axis, Y-axis, and Z-axis will be referred to as the translational (F_x), transverse (F_y), and axial force (F_z) respectively, and will be given in Newtons (N). The moment (M_z) about the axis of rotation will be referred to as the torque and given in Newton-meters (N-m) [4].

II. EXPERIMENTATION

Aluminum alloy AA 2014-T6 rolled plates each of size 30mm × 980mm × 95mm were used for FSW experiments. The chemical composition and mechanical properties of the parent metal are presented in Table 1.1

Table 1. Chemical composition and mechanical properties of AA2014-T6 [5, 6]

Element, wt. %								YS, MPa	UTS, MPa	El., %
Cu	Si	Mn	Mg	Zn	Cr	Fe	Al			
4.0	0.8	0.60	0.4	0.25	0.1	0.7	Bal	412	455	7

The plates were welded in single pass, normal to the rolling direction, with square-butt joint configuration employing vertical milling machine (Make: G. DufourMontrenil) shown in fig 1.2.



Fig. 2 Vertical Milling Machine

The initial joint configuration is obtained by securing the plates in position using mechanical clamps. The tool material used in this study is hot worked die steel (AISI H13) hardened to 50-55 HRC with chemical composition C-0.4, Cr-0.25, Mn-0.4, Mo-1.35, Si-1, V-1, and Fe-balance (allelements in wt.%) [6].

The range of parameters selected as per the quality of weld obtained during trial experiment is shown in table 1.2.

Table 2 Welding parameters and their levels

Symbol	Welding parameter	Unit	Level 1	Level 2	Level 3
A	Rotational Speed	Rpm	710	900	1180
B	Weld Speed	mm/min	49	83	108
C	Tilt Angle	Degree	2	3	4

Design of experiments is a method of designing experiments, in which only selected number of experiments are to be performed [4]. For example if there are three parameters with three levels of each parameter, then the total number of experiments to be performed is $3^3 = 27$ experiments. But using design of experiments method, only 9 experiments are required to be performed. On the basis of these 9 experiments, the significance and optimal levels of each parameter is obtained [8, 9].

Table 3 Experimental layout using an L₉ orthogonal array

Experiment number	Welding Parameter		
	Rotational Speed (rpm)	Weld Speed (mm/min)	Tilt Angle (°)
1	710	49	2
2	710	83	3
3	710	108	4
4	900	49	3
5	900	83	4
6	900	108	2
7	1180	49	4
8	1180	83	2
9	1180	108	3

All the nine experiment perform using newly design tool shown in fig. 1.2. This tool design by combining the features of square and tapered cylindrical tool pin profile



Fig 3 Design of tool.

After welding, the FSW plates were sectioned perpendicular to the weld direction for tensile testing. Transverse tensile specimens were prepared according to the ASTM-E23.

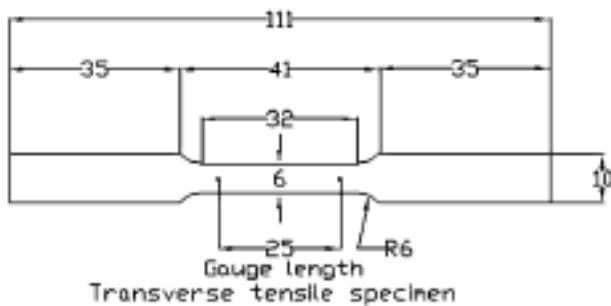


Fig. 4 Transverse Tensile Specimen

Figure 1.3 illustrates schematically the configuration of different tensile specimens used in the present study and the locations from which they were extracted.

III. RESULT AND DISCUSSION

A. Effect of Tool Pin Profile on the Appearance of the Weld:

Table 4 shows the macrostructure of the weld surfaces produced using newly design tool profile.

Table 4 Macrostructure of the weldments

Sr. no.	Condition	Macrostructure	Name of defect
1	710-49-2		No macro porosity, crack observed.
2	710-83-3		No macro porosity, crack observed.
3	710-108-4		Visible pinhole at the bottom portion of the weld at retreating side
4	900-49-3		No macro porosity, crack observed.
5	900-83-4		Tunnel defect
6	900-108-2		Tunnel defect
7	1180-49-4		Tunnel defect
8	1180-83-2		No macro porosity, crack observed.
9	1180-108-3		Tunnel defect

From the above result it is observed that the condition 1, 4, 8 shows defect free weld surface as shown in fig. due to sufficient amount of heat generated during welding. Other weld sample shows defects like pin hole and tunnel as shown in fig.

B. Effect of Tool Pin Profile on the tensile strength:

Table 5 shows the tensile strength of nine weld samples.

Table 5 Tensile Strength of weldments

Sr.no.	Condition	UTS (N/mm ²)		Avg.
		Trial 1	Trial 2	
1	710-49-2	332.92	330.88	331.90
2	710-83-3	101.46	155.2	128.33
3	710-108-4	184.22	142.70	163.46
4	900-49-3	265.45	226.62	246.04
5	900-83-4	127.19	99.64	113.42
6	900-108-2	130.72	58.57	94.65
7	1180-49-4	93.33	125.94	109.64
8	1180-83-2	260.6	216.24	238.42
9	1180-108-3	113.22	69.4	91.31

From the above obtained result it is clear that the parameters 710-49-2 shows the highest tensile strength among the other weldments.

IV. CONCLUSIONS

From the results of this present investigation and the discussion presented in the earlier chapters, the following conclusions are drawn.

- I. Tool rotation speed of 710 rpm shows the finer grain structure in macrostructural observation.
- II. Lower weld speed 48 mm/min shows highest tensile strength due to finer grain structure observed in the nugget region.
- III. Lower tilt angle 2° shows highest tensile strength because a suitable tilt of the spindle towards the trailing direction ensures that the shoulder of the tool holds the stirred material by the pin and moves the material efficiently from the front to the back of the pin

ACKNOWLEDGMENT

And finally this day has come. I am presenting the paper with great pride. There are too much efforts of gardener to yield the beautiful flowers. So we should not forget him while praising flower. It is a matter of gratification for me to pay my respects and acknowledgements to all those who have imparted knowledge and helped me to complete my report.

I would first like to acknowledge the great contribution and support I have received in this endeavor from Guide Prof. B. R. Borkar and Head of Dept. Prof. R. S. Tajane.

His in depth guidance and inspiration for me will be of great help to tackle any kind of problems likely to be met in the future.

I much obliged towards all the staff members, librarians, and my friends those supported directly and indirectly. I will keep my improvement curve on the rise and thereby enhance the reputation of my College.

REFERENCES

1. P.Rohilla and N.Kumar, "Experimental investigation of Tool Geometry on Mechanical Properties of Friction Stir Welding of AA6061", International Journal of Engineering Research & Technology Vol-3, (August 2013).
2. 1. Rajiv S. Mishra, Center for Friction Stir Processing, University of Missouri-Rolla Murray W. Mahoney, Rockwell Scientific Company, "Friction Stir welding and processing", ASM International, www.asminternational.org, pp 1-5, 2007.
3. A.K.Hussain and S.A.P.Quadri, "Evaluation of Parameters of Friction Stir Welding For Aluminum AA 6351 Alloy", International Journal of Engineering Science and Technology, Vol. 2, (2010).
4. Daniela Lohwasser and Zhan ChenS. "Friction Stir Welding", Woodhead publishinglimited, www.woodheadpublishingindia.com, pp 10-20, 2010
5. Rajakumar, C.Muralidharan, V.Balasubramanian, "Influence of friction stir welding process and tool parameters on strength properties of AA7075-T6 aluminum alloy joints", Department of Manufacturing Engineering, Annamalai University,(August 2010).
6. Yan-hua Z. T, San-bao L, Lin W, Fu-xing Q, The influence of pin geometry on bonding and mechanical properties in friction stir weld 2014 Al alloy. Materials Letter 59: 2948 – 2952, (2005).
7. K. Ramanjaneyulu, G. Madhusudhan Reddy, A. VenugopalRao, and R. Markandeya, "Structure-Property Correlation of AA 2014-T6 Friction Stir Welds: Role of Tool Pin Profile", JMEPEG 22:2224–2240, (2013).
8. M.Jayaraman, R.Sivasubramanian, V.Balasubramanian and A.K.Lakshminarayanan, "Optimization of process parameter for friction stir welding of cast aluminum alloy A319 by Taguchi method" vol.68, pp.36-43, (2009).
9. P.MuraliKrishna,N. Ramanaiah and K. PrasadaRao,"Optimization of process parameters for friction Stir welding of dissimilar Aluminum alloys (AA2024 -T6 and AA6351-T6) by using Taguchi method",pp. 71-80,(2013).
10. H. S. Patil and S. N. Soman, "Experimental study on the effect of welding speed and tool pin profiles onAA6082-O aluminum friction stir welded butt joints", International Journal of Engineering, Science and Technology, Vol. 2, pp. 268-275,(2010).